



# Leather — Physical and mechanical tests — Determination of tensile strength and percentage extension

*Cuir — Essais physiques et mécaniques — Détermination de la résistance à la traction et du pourcentage d'allongement*

[Revision of second edition (ISO 3376:2002)]

ICS 59.140.30

## ISO/CEN PARALLEL PROCESSING

This draft has been developed within the European Committee for Standardization (CEN), and processed under the **CEN-lead** mode of collaboration as defined in the Vienna Agreement.

This draft is hereby submitted to the ISO member bodies and to the CEN member bodies for a parallel five-month enquiry.

Should this draft be accepted, a final draft, established on the basis of comments received, will be submitted to a parallel two-month approval vote in ISO and formal vote in CEN.

**This draft International Standard is submitted to all ISO member bodies for voting, as a standard prepared by an international standardizing body in accordance with Council Resolution 42/1999. The proposer, *Physical Test Commission of the International Union of Leather Technologists and Chemists Societies (Commission IUP, IULTCS)*, has been recognized by the ISO Council as an international standardizing body for the purpose of Council Resolution 42/1999.**

**To expedite distribution, this document is circulated as received from the committee secretariat. ISO Central Secretariat work of editing and text composition will be undertaken at publication stage.**

**Pour accélérer la distribution, le présent document est distribué tel qu'il est parvenu du secrétariat du comité. Le travail de rédaction et de composition de texte sera effectué au Secrétariat central de l'ISO au stade de publication.**

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**Copyright notice**

This ISO document is a Draft International Standard and is copyright-protected by ISO. Except as permitted under the applicable laws of the user's country, neither this ISO draft nor any extract from it may be reproduced, stored in a retrieval system or transmitted in any form or by any means, electronic, photocopying, recording or otherwise, without prior written permission being secured.

Requests for permission to reproduce should be addressed to either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Reproduction may be subject to royalty payments or a licensing agreement.

Violators may be prosecuted.

## Contents

Page

Foreword .....	iv
1 Scope .....	1
2 Normative references .....	1
3 Principle .....	1
4 Apparatus .....	1
5 Sampling and sample preparation .....	2
6 Procedure .....	3
6.1 Determination of dimensions .....	3
6.2 Determination of tensile strength .....	3
6.3 Determination of the percentage elongation caused by a specified load .....	3
6.4 Determination of the percentage elongation at break .....	3
6.5 Slippage .....	3
7 Expression of results .....	4
7.1 Tensile strength .....	4
7.2 Percentage elongation caused by a specified load .....	4
7.3 Percentage elongation at break .....	4
8 Test report .....	4

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 3376/IUP6 was prepared by the Physical Test Commission of the International Union of Leather Technologists and Chemists Societies (IUP Commission, IULTCS) in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 289, *Leather*, the secretariat of which is held by UNI, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first (EN ISO 3376:2002), which has been technically revised.

# Leather — Physical and mechanical tests — Determination of tensile strength and percentage extension

## 1 Scope

This International Standard specifies a method for determining the tensile strength, elongation at a specified load and elongation at break of leather. It is applicable to all types of leather.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2418, *Leather - Chemical, physical and mechanical and fastness tests - Sampling location*

ISO 2419, *Leather - Physical and mechanical tests - Sample preparation and conditioning*

ISO 2589, *Leather - Physical and mechanical tests - Determination of thickness*

ISO 7500-1:2004, *Metallic materials – Verification of static uniaxial testing machines – Part 1: Tension/compression testing machines – Verification and calibration of the force-measuring system*

## 3 Principle

A test piece is extended at a specified rate until the forces reach a predetermined value or until the test piece breaks.

## 4 Apparatus

### 4.1 Tensile testing machine, with:

- a force range appropriate to the specimen under test;
- a means of recording the force to an accuracy of at least 2 % as specified by Class 2 of ISO 7500-1;
- a uniform speed of separation of the jaws of 100 mm/min  $\pm$  20 mm/min;
- a means of recording the force - e.g. as an extension curve;
- jaws, minimum length 45 mm in the direction of the applied load, designed to apply constant clamping by mechanical or pneumatic means. The texture and design of the inside faces of the jaws shall be such that at the maximum load attained in the test the specimen does not slip at either jaw by an amount exceeding 1 % of the original jaw separation.

4.2 **A means of determining the extension of the test piece**, either by monitoring the separation of the jaws or by sensors which monitor the separation of two fixed points on the test piece.

4.3 **Thickness gauge**, as specified in ISO 2589.

4.4 **Press knives**, as specified in ISO 2419 capable of cutting a test piece as shown in Figure 1 with dimensions as given in Table 1.

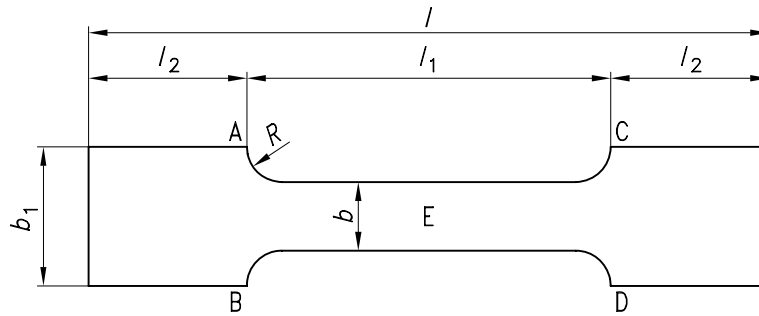


Figure 1 — Shape of test piece

Table 1 — Dimensions of test pieces

All dimensions in millimetres

Designation	$l$	$l_1$	$l_2$	$b$	$b_1$	$R$
Standard	110	50	30	10	20	5
Large	190	100	45	20	40	10

4.5 **Vernier callipers**, reading to 0,1 mm.

## 5 Sampling and sample preparation

5.1 Sample in accordance with ISO 2418.

5.2 From the sample, cut six test pieces in accordance with ISO 2419 by applying a press knife (4.4) to the grain surface, three test pieces with the longer sides parallel to the backbone and three test pieces with the longer sides perpendicular to the backbone. If previous testing has shown that there is slippage of the test piece in the jaws, use the large press knife (4.4).

NOTE If there is a requirement for more than two hides or skins to be tested in one batch, then only one test piece in each direction need be taken from each hide or skin, provided that the overall total is not less than three test pieces in each direction.

5.3 Condition the test pieces in accordance with ISO 2419.

## 6 Procedure

### 6.1 Determination of dimensions

**6.1.1** Using vernier callipers (4.5) measure the width of each test piece to the nearest 0,1 mm at three positions on the grain side and three on the flesh side. In each group of three measurements make one at the mid-point E (as shown in Figure 1) and the other two at positions approximately mid-way between the mid-point E and the lines AB and CD. Take the arithmetic mean of the six measurements as the width of the test piece,  $w$ .

NOTE For soft ("flexible") leather, the width may be taken as the width of the press knife.

**6.1.2** Measure the thickness of each test piece in accordance with ISO 2589. Make the measurements at three positions namely the mid-point E and at positions approximately mid-way between the mid-point E and the lines AB and CD. Take the arithmetic mean of the three measurements as the thickness of the test piece,  $t$ .

### 6.2 Determination of tensile strength

**6.2.1** Set the jaws of the tensile strength testing apparatus (4.1)  $50 \text{ mm} \pm 1 \text{ mm}$  apart if using the standard test piece or 100 mm if using the large test piece. Clamp the test piece in the jaws so that the edges of the jaws lay along the lines AB and CD. When the test piece is clamped, ensure its grain surface lies in one plane. The length axis shall be parallel to the traction direction.

**6.2.2** Run the machine until the test piece breaks and record the highest force exerted as the breaking force,  $F$ .

### 6.3 Determination of the percentage elongation caused by a specified load

**6.3.1** Clamp the test piece between the jaws of the apparatus as described in 6.2.1. Measure the distance between the jaws at least to the nearest 0,5 millimetres and record this distance,  $L_0$ , as the initial length of the test piece for the purpose of the test.

**6.3.2** Start the test. Unless the apparatus automatically draws a force/extension curve with the necessary accuracy (see 4.2), follow the distance between the pairs of jaws or the sensors as the force increases.

**6.3.3** Note the distance in millimetres between the pair of jaws or sensors at the instant when the force first reaches the specified value. This distance represents the length of the test piece at this force,  $L_1$ . Do not stop the apparatus if results from the procedures described in 6.2 or 6.4 are also required.

### 6.4 Determination of the percentage elongation at break

**6.4.1** Carry out the steps given in 6.3.1.

**6.4.2** Run the tensile test machine until the test piece breaks.

**6.4.3** Record the distance between the jaws or sensors at the instant when rupture of the test piece occurs.

This distance represents the length of the test piece at break,  $L_2$ .

### 6.5 Slippage

If there is slippage of the test piece at either jaw when tested according to 6.2, 6.3 or 6.4, and the slippage is greater than 1 % of the initial jaw separation, reject the result and repeat the determination with a new test piece cut using the large press knife (4.4).

## 7 Expression of results

### 7.1 Tensile strength

The tensile strength,  $T_n$ , in MPa (or Newton per square millimetre if required) shall be calculated using the equation:

$$T_n = \frac{F}{w \times t}$$

where

$F$  is the highest force recorded in Newton;

$W$  is the mean width of the test piece in millimetres;

$t$  is the mean thickness of the test piece in millimetres.

NOTE The relationship between MPa and  $N/mm^2$  is the following:  $1 N/mm^2 = 1 MPa$

### 7.2 Percentage elongation caused by a specified load

The percentage elongation caused by a specified load,  $E_1$ , shall be calculated using the equation:

$$E_1 = \frac{L_1 - L_0}{L_0} \times 100$$

where

$L_1$  is the separation of the jaws or sensors at the specified load;

$L_0$  is the initial separation of the jaws or sensors.

### 7.3 Percentage elongation at break

The percentage elongation at break,  $E_b$ , shall be calculated using the equation:

$$E_b = \frac{L_2 - L_0}{L_0} \times 100$$

Where

$L_2$  is the separation of the jaws or sensors at break;

$L_0$  is the initial separation of the jaws or sensors.

## 8 Test report

The test report shall include the following:

- a) reference to this International Standard, i.e. ISO 3376;
- b) the mean tensile strength in MPa (or Newton per square millimetre) to the nearest 0,1 MPa, for the test pieces with the longer edge cut parallel to the backbone;

- c) the mean tensile strength in MPa (or Newton per square millimetre) to the nearest 0,1 MPa, for the test pieces with the longer edge cut perpendicular to the backbone;
- d) the mean percentage elongation at break to the nearest 1%, for the test pieces with the longer edge cut parallel to the backbone;
- e) the mean percentage elongation at break to the nearest 1%, for the test pieces with the longer edge cut perpendicular to the backbone;
- f) the mean percentage elongation at a specified load to the nearest 1%, for the test pieces with the longer edge cut parallel to the backbone; if required;
- g) the mean percentage elongation at a specified load to the nearest 1%, for the test pieces with the longer edge cut perpendicular to the backbone; if required;
- h) the thickness of the sample in mm in accordance with ISO 2589;
- i) any deviations from the method specified in this International Standard;
- j) full details for identification of the sample and any deviation from ISO 2418 with respect to sampling.
- k) If required by customer or in specifications it is allowed to report the results described in 8 k), 8 l) and 8 m) instead of 8 b) to 8 g);
- l) the average tensile strength in MPa (or Newton per square millimetre) to the nearest 0,1 MPa (i.e., the arithmetic mean of b and c);
- m) the average percentage elongation at break to the nearest 1% (i.e., the arithmetic mean of d and e);
- n) the average percentage elongation at a specified load to the nearest 1% (i.e., the arithmetic mean of f) and g); if required;
- o) the standard atmosphere used for conditioning and testing as given in ISO 2419.